




# Huron Bluestone Data Sheet

## Wet Slip Resistance

Finish	Value	Classification
Sandblasted	65 ( $\pm 2$ )	P5
Bush Hammered	59 ( $\pm 2$ )	P5
Scratched	70 ( $\pm 2$ )	P5
Leather	47 ( $\pm 2$ )	P4
Honed	39 ( $\pm 2$ )	P3

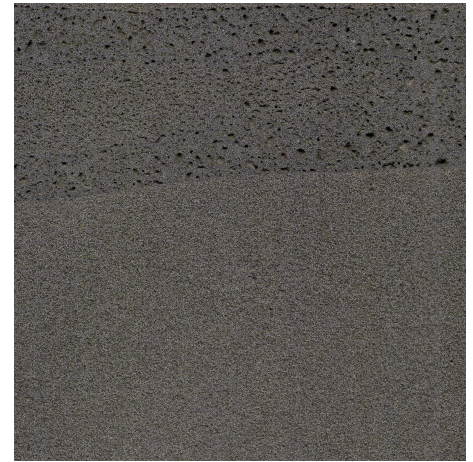

FINISH &gt; SANDBLASTED

## Analysis

## Results

Abrasion Resistance (Ha)	36.9 ( $\pm 0.6$ )
Bulk Specific Gravity (Kg/m <sup>3</sup> )	2.716 ( $\pm 2$ )
Flexural Strength (MPa)	
Average Dried	12.3 ( $\pm 0.2$ )
Average Soaked	12.7 ( $\pm 0.2$ )
Luminous Reflectance - Sandblasted Finish	
Average Dried (Yd)	19.3
Average Soaked (Yw)	5.8
Modulus of Rupture (MPa)	
Average Dried	14.3 ( $\pm 0.2$ )
Average Soaked	15.9 ( $\pm 0.2$ )
Resistance to Salt Attack (%)	0.45 ( $\pm 0.03$ )
Solar Reflectance Index	
High Wind	15.3 ( $\pm 1.6$ )
Unconfined Compressive Strength (MPa)	
Average Dried	114 ( $\pm 1.4$ )
Average Soaked	84 ( $\pm 1.0$ )
Water Absorption (%)	
Average by Volume	2.81 ( $\pm 0.08$ )
Average by Weight	1.04 ( $\pm 0.03$ )

Disclaimer: Due to the inherent variability of natural stone, the results are indicative.